

Full paper

Optimized mesopores enabling enhanced rate performance in novel ultra-high surface area meso-/micro-porous carbon for supercapacitors

Jie Yang¹, Hao Wu¹, Min Zhang, Wei Ren, Yuan Liu, Haibiao Chen*, Feng Pan*

¹ School of Chemistry and Chemical Engineering, Shanghai Jiao Tong University, Shanghai 200240, China; ² School of Materials Science and Engineering, Shanghai Jiao Tong University, Shanghai 200240, China; ³ School of Chemistry, Shanghai Jiao Tong University, Shanghai 200240, China; ⁴ School of Chemistry and Chemical Engineering, Shanghai Jiao Tong University, Shanghai 200240, China; ⁵ School of Chemistry and Chemical Engineering, Shanghai Jiao Tong University, Shanghai 200240, China; ⁶ School of Chemistry and Chemical Engineering, Shanghai Jiao Tong University, Shanghai 200240, China

ARTICLE INFO

Keywords:
Mesoporous carbon
Ion-exchange template
Polystyrene
Supercapacitors
High energy density

ABSTRACT

Increasing both the energy density and the power density of supercapacitors is an important but challenging research subject. Porous carbon with extremely high surface area, such as activated carbon, is a key engineering material for current supercapacitor technology. Here we report optimized mesopores enabling significantly enhanced rate performance in hierarchically meso-/micro-porous carbon with a ultra-high surface area for supercapacitors, which is prepared by a new ion-exchange template method to exhibit a high mesopore volume proportion (66.0%), as well as a large pore volume up to $2.47 \text{ cm}^3 \text{ g}^{-1}$, and an ultra-high specific surface area of $3122 \text{ m}^2 \text{ g}^{-1}$. Polystyrene was used as a precursor to produce mesoporous SiOC, and sequentially NaOH was used to activate SiOC to produce highly porous carbon by removing silica and activating carbon. Hierarchically porous carbon C800 exhibited a high energy density up to 42 Wh kg^{-1} at a power density of 374 W kg^{-1} , and still retained an energy density of 21 Wh kg^{-1} at a high power density of 30 kW kg^{-1} . The superior rate performance of the supercapacitor is attributed to that C800 contains an anisotropic distribution of mesopores which facilitate fast ion migration during high-power charging/discharging.

1. Introduction

Electricity generated from renewable resources such as solar energy, wind power, and biofuel is envisioned to power a green and more sustainable future. Rechargeable batteries, especially lithium batteries, are one of the most important energy storage devices enabling on-site utilization of the electrical energy. Supercapacitors to rechargeable batteries, supercapacitors fill the gap in the energy storage scheme with exceptional power density [1,2]. In general, supercapacitors can be classified into two categories: electrical double-layer capacitors (EDLCs) based on charge storage at the electrode/electrolyte interface and pseudocapacitors through reversible redox reactions [1–3]. EDLCs based on porous carbons have recently attracted tremendous attention due to the high power density and almost unlimited cycle life [4,5]. However, the much low energy densities (approximately 5 Wh kg^{-1}) of commercial EDLCs have hindered their wide applications [6–9]. Owing to its super high surface area and electrical conductivity, porous carbon is an ideal material for EDLCs. Generally, the performance of carbon materials in EDLCs is highly dependent on the migration and adsorption of ions inside mesopores, which are largely determined by the pore structure of the material [10–12].

Traditionally, activated carbons have been the choice of the electrode materials in EDLCs. Activated carbons are produced by either physical or chemical activation of carbon precursors [13–22]. Typical activated carbon materials are predominantly micro-porous (pore width $< 2 \text{ nm}$) and the specific surface area can exceed $3000 \text{ m}^2 \text{ g}^{-1}$. However, micro-pores are not easily accessible to large ions when the electrolyte is organic ionic liquid, which can work at a higher operating voltage with a higher energy density but a lower power density due to slow mass transfer [23–32]. Introducing mesopores (pore width of $2\text{--}50 \text{ nm}$) to porous carbon can improve effective utilization of the pore surface area and accelerate mass transfer so as to enhance the power density. Usually, increasing the pore size leads to the reduction of the specific surface area if the specific pore volume remains constant. To optimize porous carbon materials for maximum effective surface area, both the specific surface area and the specific pore volume will need to be increased simultaneously [33].

One approach to produce mesoporous carbon is to use unconventional precursors with the conventional activation process. Recently, activated graphene synthesized by KOH activation following microwave expansion was found to be highly mesoporous with a specific surface area exceeding $3000 \text{ m}^2 \text{ g}^{-1}$ [8,34]. Another approach to introduce pores with controlled pore size distribution is to integrate sacrificial

* Corresponding authors.

E-mail addresses: chenhb@sjtu.edu.cn (H. Chen), panfeng@sjtu.edu.cn (F. Pan).

¹ These authors contributed equally to this work.

... templates into the carbon precursors [35,36]. However, using an additional sacrificial template complicates the process and increases the materials cost. Alternatively, porous carbon can be produced from carbon-forming alloys or ceramics with a homogeneous nanostructure by selectively removing the non-carbon phases. Gogotsi's group produced carbide derived carbons (CDCs) using a combination process with precise control of the pore size, and successfully applied the materials for supercapacitors [24,25,30] and hydrogen and methane storage [37]. Pena-Alonso et al. showed that silicon oxycarbide (SiOC) ceramics can be etched by hydrofluoric (HF) acid to form porous carbon materials with specific surface area up to 600 m² g⁻¹ [38]. In these methods, toxic chemicals were used to etch the carbon precursor to produce pores, which will be a concern for large scale production.

In this article we report a new class of hierarchically meso-/microporous carbon materials produced from polystyrene precursors using a simple alkaline activation process. Polystyrenes have long been used as precursors to produce SiOC ceramics. Upon pyrolysis of polystyrene, silica and carbon atoms rearrange and phase segregate into a homogeneous nanoscale structure containing silica nanodomains dispersed in a graphitic network [39]. Selectively removing one phase will create pores in the structure, as demonstrated by Gogotsi's group [40,41] and Pena-Alonso et al. [38]. We extend the concept by using SiOC to produce carbon materials with very high surface area employing an alkaline activation process, and especially introducing a very large mesopore volume. In comparison to mainly micropores in traditional activated carbon, the optimized mesopores in the hierarchically porous carbon in this work achieved both maximum effective surface area and fast mass transfer, by bridging the micropores and the external environment. The value of this carbon material with unique pore structure and properties was demonstrated in EDLC application. The EDLCs employing the polystyrene-derived carbon showed a high specific capacitance and excellent rate performance, demonstrating both high energy density and power density.

2. Material and methods

2.1. Synthesis of polystyrene-templated carbon

The synthesis of polystyrene-derived carbon is schematically illustrated in Scheme 1. Polystyrene elastomer was prepared by addition polymerization of vinyl terminated phenylmethyl polystyrene using phenylmethylhydrosilane (PMHS) as a cross-linker. The purpose of selecting phenylmethyl precursor was to obtain a high carbon content and improve the product yield. In a typical procedure, 20 g of vinyl terminated phenylmethyl polystyrene (UC252, viscosity 3000 mPa·s, Jiangsu United Chemistry, China) and 1 g of PMHS (Sigma-Aldrich) were reacted with the addition of 15 µL 2 wt% Pt

catalyst solution (platinum(0)-1,3-divinyl-1,1,3,3-tetramethylsiloxane complex solution in xylene, Sigma-Aldrich) at room temperature. The cross-linked polymer was pyrolyzed in a tube furnace (MTI Corporation) under argon flow. The furnace was heated from room temperature to 1200 °C at 10 °C/min ramp rate and held at 1200 °C for one hour before cooling down to room temperature at 10 °C/min ramp rate. The polymer-ceramic conversion was accompanied by 44% weight loss (Fig. S2) due to loss of hydrogen, volatile hydrocarbons, and silanes. The resulted SiOC ceramic was designated as SiOC1200. The bulk composition of SiOC1200 can be described as SiO_{0.9}C_{2.2} according to elemental analysis [42]. SiOC1200 was pulverized and mixed with NaOH particles in a ratio of 1:4. The mixture was placed in a nickel boat and heated in a tube furnace to a temperature range of 400–900 °C at 5 °C/min ramp rate and held at that temperature for one hour before cooling down at 5 °C/min ramp rate under argon flow. The heat treatment temperature was selected with a range from 400 through 900 °C at 100 °C intervals and the products were labelled as

unit. The surface area was calculated using the Brunauer–Emmett–Teller (BET) model and pore size distribution (PSD) was derived by a density functional theory (DFT) model based on the nitrogen adsorption data. The morphology was observed with scanning electron microscopy (SEM, ZEISS Supra 55) and transmission electron microscopy (TEM, FEI Tecnai G2 F30). The phase composition was analyzed by X-ray diffraction (XRD) using a Bruker D8 Advance diffractometer with Cu-K α radiation. Raman spectra were collected using a Horiba modular Raman system containing an Olympus BX41 microscopy, a diode laser source (wave length 532 nm, LEO Photoelectric Co., Ltd, China), a Horiba HR320 spectrometer, and a Synapse CCD detector. X-ray photoelectron spectra (XPS) were obtained using an ESCALAB 250XL X-ray photoelectron spectrometer.

2.3. Electrochemical tests

Typically, the working electrode was made of active material, conductive agent (acetylene black), and polymer binder (polytetrafluoroethylene, PTFE) in a mass ratio of 8:1:1, respectively. All the above components were mixed well and ground into a paste in mortar with addition of isopropyl alcohol. Then the paste was rolled into uniformly thin sheets (thicknesses from 100 to 150 μm) and punched into 1 cm diameter plates. The plates were dried at 120 $^{\circ}\text{C}$ for 12 h under vacuum to remove solvent, and pressed onto nickel foam to produce the work electrode. The mass loading of the active materials varied from 2 to 2.5 mg cm^{-2} . The three-electrode tests were performed in the electrolyte of 6.0 M KOH with Hg/HgO electrode as the reference electrode and Pt plate as the counter electrode. For two-electrode test, a CR2032 coin-cell type device was assembled using a pair of circular electrode plates sandwiching a Whatman separator and 1 M tetraethylammonium tetrafluoroborate/acetonitrile (TEABF $_4$ /AN) solution as the electrolyte. The cyclic voltammetry (CV) measurement and electrochemical impedance spectroscopy (EIS) test were carried out on a CHI660 electrochemical workstation (Shanghai Chenhua Instrument Co., Ltd.). The EIS data were obtained at open circuit voltage with an AC amplitude of 5 mV in the frequency range of 0.01 Hz–100 kHz. The charging/discharging tests were performed on a Maccor MC16 high-precision battery testing system. All the electrochemical tests were carried out at room temperature.

Based on the discharging curves, the specific capacitance (C) for was calculated according to the following equation:

$$C_s = \frac{I \Delta t}{m \Delta V} \quad (4)$$

where I (A) is the current, ΔV (V) is the discharging potential change minus the IR drop and Δt (s) is the discharging time corresponding to ΔV . (m) (g) represents the mass of the active materials in a single carbon electrode.

The energy density E (Wh kg^{-1}) and power density P (W kg^{-1}) were calculated from the following equations:

$$E = \frac{1}{2} C (\Delta V)^2 \quad (5)$$

$$P = \frac{E}{\Delta t} \quad (6)$$

where C (F g^{-1}) is the gravimetric capacitance, ΔV (V) is operating potential, and Δt (s) is the discharging time.

3. Results and discussion

3.1. Morphology and structure

The nitrogen adsorption/desorption isotherms of the samples are shown in Fig. 1a, and the corresponding DFT pore size distributions are shown in Fig. 1b. The isotherms of C400 and HF-etched sample can be classified as type I isotherm, which corresponds to microporous

materials, since majority of the nitrogen adsorption takes place at very low pressure range ($P/P_0 < 0.05$) via micropore filling. With the temperature increasing to 700 $^{\circ}\text{C}$ and 800 $^{\circ}\text{C}$, the adsorption volumes dramatically increase and the isotherms show obvious features of type IV isotherm. The significant hysteresis loop in the isotherm suggests that there are mesopores existing in C700 and C800. The isotherm of sample C900 displays the same feature as that of the C800, but the adsorption volume begins to decrease. For quantitative analysis, the specific surface area was derived using the BET method and the specific pore volume was obtained by taking the adsorption volume at relative pressure close to unity, shown in Table S1. It is noted that the BET specific surface area of C800 reaches maximum of 3122 $\text{m}^2 \text{g}^{-1}$ with a specific pore volume of 2.47 $\text{cm}^3 \text{g}^{-1}$. In addition, it has the highest volume proportion of mesopores at 66.0% among all the samples. The BET specific surface area, specific pore volume, and mesopore volume of C800 are all among the highest values for porous carbon materials recently reported as shown in Table S2.

The PSD shown in Fig. 1b suggests that both the micropore volume and the mesopore volume increase as the activation temperature increases within the range of 400–800 $^{\circ}\text{C}$, and decrease at 900 $^{\circ}\text{C}$. During activation, the temperature is a vital factor impacting the formation of pore structure and the value of the specific surface area. Based on the variation of PSD according to the temperature, a possible mechanism for the formation of pore structure is proposed. Compared to the process of HF-etching, mesopores were created during NaOH activation due to the etching of both silica and carbon. When the activation temperature was relatively low such as 400 $^{\circ}\text{C}$ and 500 $^{\circ}\text{C}$, the removal of silica played a dominant role without etching much carbon so that majority of the created pores were in the range of micropore. This can be confirmed by the result that the average pore sizes of C400 and C500 are similar to the size of the initial silica nanodomains in SiOC [42]. At a relatively high temperature of 800 $^{\circ}\text{C}$, the adjacent pores previously created due to silica removal were connected as the carbon walls were broken down, leading to the formation of a large number of mesopores. Although mesopores were largely created on the carbon walls, which is similar to the activation mechanism of most porous carbon materials. When the activation temperature further increased to 900 $^{\circ}\text{C}$, the BET specific surface area dropped drastically to 1646 $\text{m}^2 \text{g}^{-1}$ and the pore volume dropped to 1.33 $\text{cm}^3 \text{g}^{-1}$, probably because the pore structure partially collapsed causing reduction in pore volume and surface area. It is noted that the carbon skeleton tend to be excessively etched at a higher temperature. Also, a higher temperature facilitates the reorganization and restacking of graphene sheets, causing the elimination of inter-layer pores.

The XRD spectra of the samples are shown in Fig. 2a. The XRD spectrum of SiOC1200 shows a peak at around 26.6 $^{\circ}$, corresponding to the (002) planes of graphite. The (101) peak near 44 $^{\circ}$ is very broad and weak, suggesting misalignment between the graphene layers and a low degree of graphitization. Similar peaks are found for sample C400, although the (002) peak significantly broadens and shifts to a lower angle at around 23 $^{\circ}$. Shifting of the (002) peak corresponds to a change of the graphene layer spacing from 0.335 to 0.384 nm [42]. Highly NaOH activation caused the expansion of the layered structure, especially after the space-filling silica phase was removed. In the XRD pattern of C800, the (002) peak almost disappears and only a broad (101) peak is visible. When activated at 800 $^{\circ}\text{C}$, carbon started to lose its ordered structure as it became highly porous due to vigorous NaOH etching [34]. The (002) peak reappears in the XRD pattern of C900, suggesting reconstruction of the structure takes place at this temperature. Inevitably, crystallization of the structure leads to elimination of pores and reduction of the specific surface area, as previously shown in the pyrolysis measurement. The Raman spectra of the materials are shown in Fig. 2b. The D band near 1340 cm^{-1} originates from the 6-fold ring breathing mode vibration, which is only possible at free edges. G band near 1580 cm^{-1} originates from the in-plane stretching mode vibration. The ratio of the intensity of D band to the

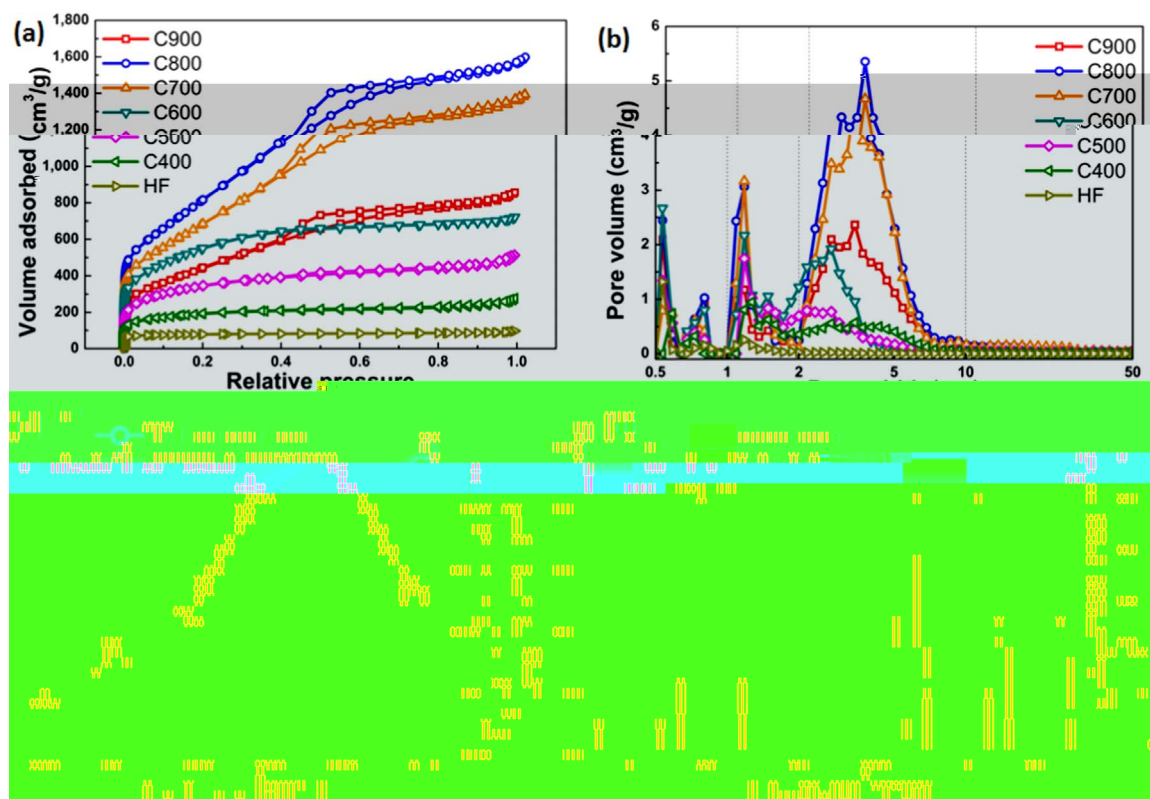


Fig. 1. (a) Nitrogen adsorption-desorption isotherms of polysiloxane-derived carbon; (b) DFT pore size distribution; (c) BET specific surface area and specific pore volume vs. activation temperature; (d) Composition of macropores, mesopores, and micropores vs. activation temperature.

Intensity of G band (I_D/I_G) is commonly used to estimate the defect population or crystallite size of carbon materials [47,48]. The I_D/I_G values of SiOC1200, C400, C500, C600, C700, C800, and C900 are 1.16, 0.84, 0.91, 1.01, 1.10, 1.08, and 1.09, respectively. The Raman result suggests that carbon in SiOC1200 has the highest density of free edges, or defects, although SiOC1200 is amorphous at all. After removal of the silicic acid, the graphene layers appeared to reorganize and the number of defects decreased, although pores were being created at the same time. As the activation temperature increased, both reorganization and attacking of carbon became more significant, with the former eliminates defects while the latter produced defects. More reorganization took place during the formation of C900, with 2D peak appears as an indication of stacking of several graphene layers.

The surface compositions of C800 as investigated by XPS are shown in Fig. 2c and d. The XPS analysis reveals that the samples are mainly composed of C (ca. 89.14 wt%) and O (ca. 9.84 wt%) with a small amount of Si (ca. 1.02 wt%), which is in good agreement with the TGA result. The high-resolution C1s spectrum can be deconvoluted into three peaks assigned to the C-C/C=C bond (~284.8 eV), C-O (~285.5 eV), and C=O (~288.9 eV), respectively [49–51]. The high-resolution O1s spectrum can be fitted to two peaks corresponding to C=O (531.6 eV) and C-O (532.9 eV) [52,53]. The abundant presence of O functional groups in the prepared materials can facilitate the wettability of the electrode, leading to an effective mass transfer.

The morphology of the polysiloxane-derived carbon materials as observed by SEM and TEM are shown in Fig. 2e and f. SiOC1200 appears to have amorphous morphology under SEM. Fig. 2f displays a sponge-like morphology of C800 with abundant macro/micropores. The corresponding inset of TEM further reveals that several layers of graphitized carbon form the twisted crystalline domains containing lots of defects [22].

3.2. Electrochemical performance

In the three-electrode tests, the specific capacitance was found to be almost proportional to the specific surface area, and the area-normalized specific capacitance was around $10 \mu\text{F cm}^{-2}$ (Figs. S5 and S6). C800 demonstrated the highest specific capacitance and superior rate performance owing to its highest specific surface area and a large volume of mesopores among all samples. The cyclic voltammetry (CV) measurement of C800 performed using various scanning rates from 5 to 200 mV/s in voltage range of -1.0 to 0 V is shown in Fig. 3a. The CV curves show a quasi-rectangular shape at different scanning rates, indicating a typical characteristic of double-layer capacitor behavior and a superior rate capability. The EDLC was further tested at various charging/discharging current densities, shown in Fig. 3b. The charging/discharging curves are close to symmetric triangle and show a very small voltage drop, suggesting a low resistance and the efficient double-layer charge storage. The specific capacitance of the materials was calculated from the charging/discharging measurements. As shown in Fig. 3c, a high specific capacitance of 327 F g^{-1} is achieved at a current density of 0.5 A g^{-1} . Even at a high current density of 50 A g^{-1} , the specific capacitance is still as high as 198 F g^{-1} , which is among the best reported performances based on carbon materials [1,54–57]. The cycling stability of the EDLC was tested at 5 A g^{-1} for 10,000 cycles. After 10,000 cycles, the capacitance retention is still as high as 93.9%, showing that the material has excellent stability.

These results suggest that the beneficial hierarchical pore layout of C800 can facilitate fast response and charge transfer, leading to a superior rate performance, which is further revealed by electrochemical impedance spectroscopy (EIS) in Fig. S8. The Nyquist plot indicates that the C800 shows a nearly ideal capacitive behavior with a small equivalent series resistance of 0.40Ω , which contains the resistance of

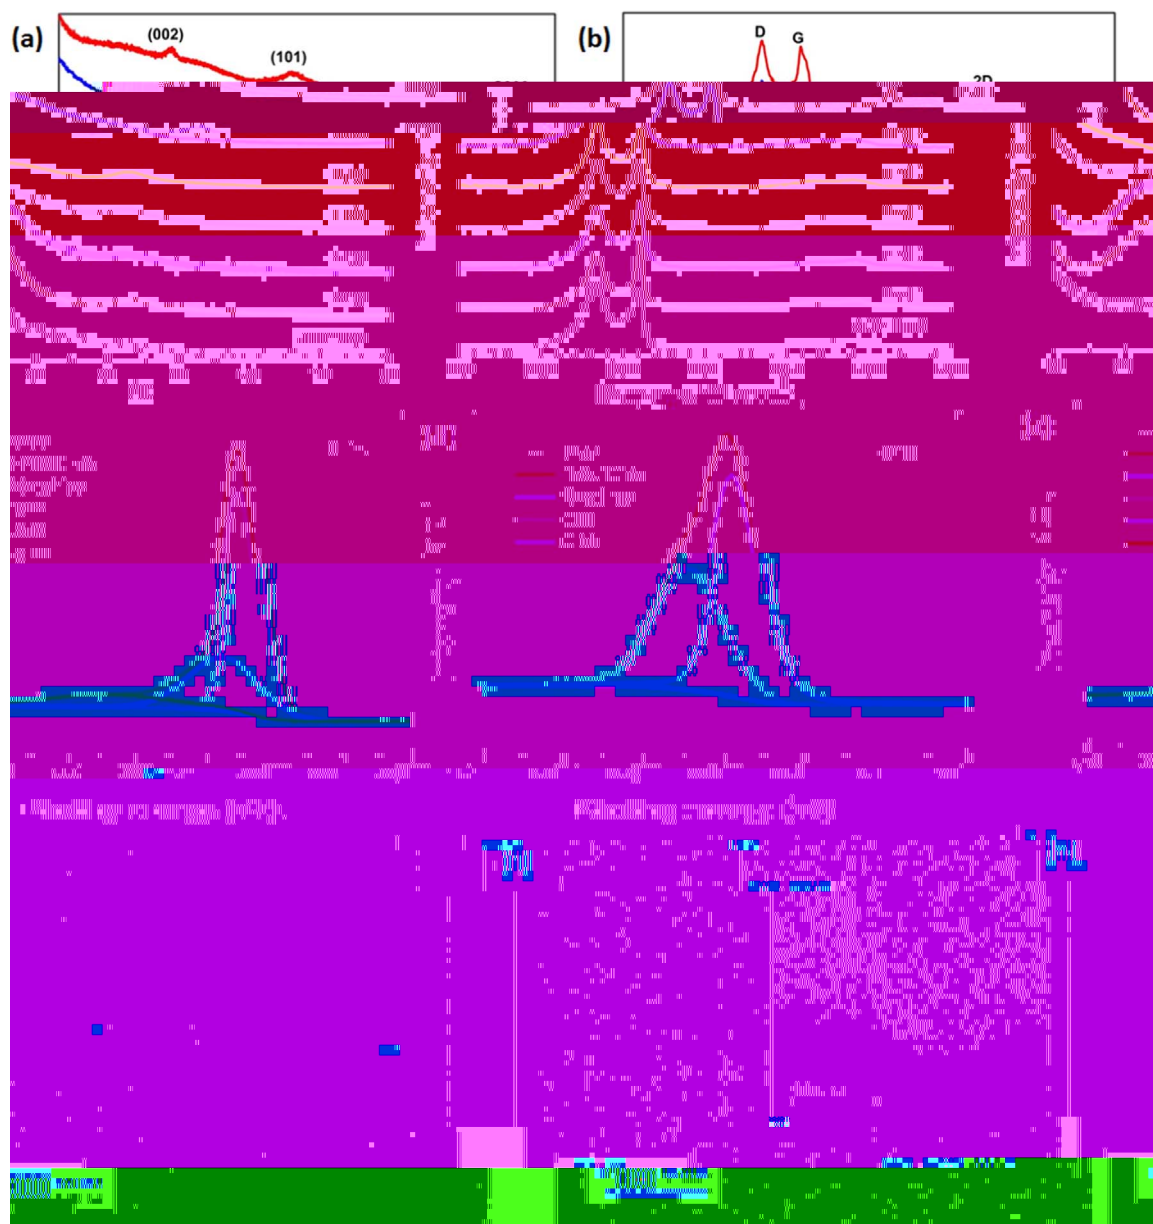


Fig. 2. (a) XRD of SIOC-1200, C400-C900; (b) Raman spectra of SIOC-1200, C400-C900; (c) High-resolution C 1s XPS spectra of C800; (d) High-resolution O 1s spectra of C800; (e) SEM of SIOC-1200; (f) SEM of C800 and TEM of C800 (inset).

the active material, the resistance of the electrolyte and contact resistance at the interface. In the high-frequency region, the small semicircle with a diameter of $0.89\ \Omega$ means a low charge-transfer resistance in the active material. A nearly vertical slope at the low-frequency region reveals the excellent pore accessibility for the electrolyte and fast response [9,57,58].

In the two-electrode test in symmetrical EDLCs with TEABF₄/AN electrolyte, the CV was measured in a voltage range of 0–2.5 V using various scan rates as shown in Fig. 3c. The CV curves are also close to rectangular shapes, suggesting a typical EDLC behavior. Meanwhile, charging/discharging curves (shown in Fig. 3d) display a highly symmetric triangular shape, indicating an excellent EDLC behavior. As shown in Fig. 3e, the specific capacitance is $163\ \text{F g}^{-1}$ at a current density of $0.5\ \text{A g}^{-1}$, and it gradually decreases as the current density increases. At a current density of $50\ \text{A g}^{-1}$, the specific capacitance is about $129\ \text{F g}^{-1}$. The cycle performance of the EDLC in the organic electrolyte was measured at $2\ \text{A g}^{-1}$ for 10,000 cycles. At the end of the test, the capacity retention was at 90.3%.

The performance of C800 is compared to YP50 as shown in Figs. S9 and S10. YP50 is also a meso-/microporous material with a lower specific surface area and a lower mesopore volume proportion (See Table S1 and Fig. S3). In the organic electrolyte, C800 showed much higher gravimetric specific capacitance and also higher capacitance retention in comparison to YP50. The result suggests that a large mesopore volume is essential for facilitating ion transport within the porous electrode material. The fitting EIS data in Fig. S8 show that the equivalent series resistance (ESR) and the charge-transfer resistance of YP50 are $0.51\ \Omega$ and $1.10\ \Omega$, respectively, which are both higher than those of C800, suggesting that there is a lower diffusion resistance and charge-transfer resistance in C800. To further increase the energy density, the voltage was increased to 3 V, shown in Fig. S10 and S11, C800 continued to demonstrate excellent capacitance retention even at this high voltage. A Ragone plot was generated for these materials and shown in Fig. 4a. C800 shows a maximum energy density of $31\ \text{Wh g}^{-1}$ at a power density of $311\ \text{W g}^{-1}$ when tested at 2.5 V, and a maximum energy density of $42\ \text{Wh g}^{-1}$ at a power density of

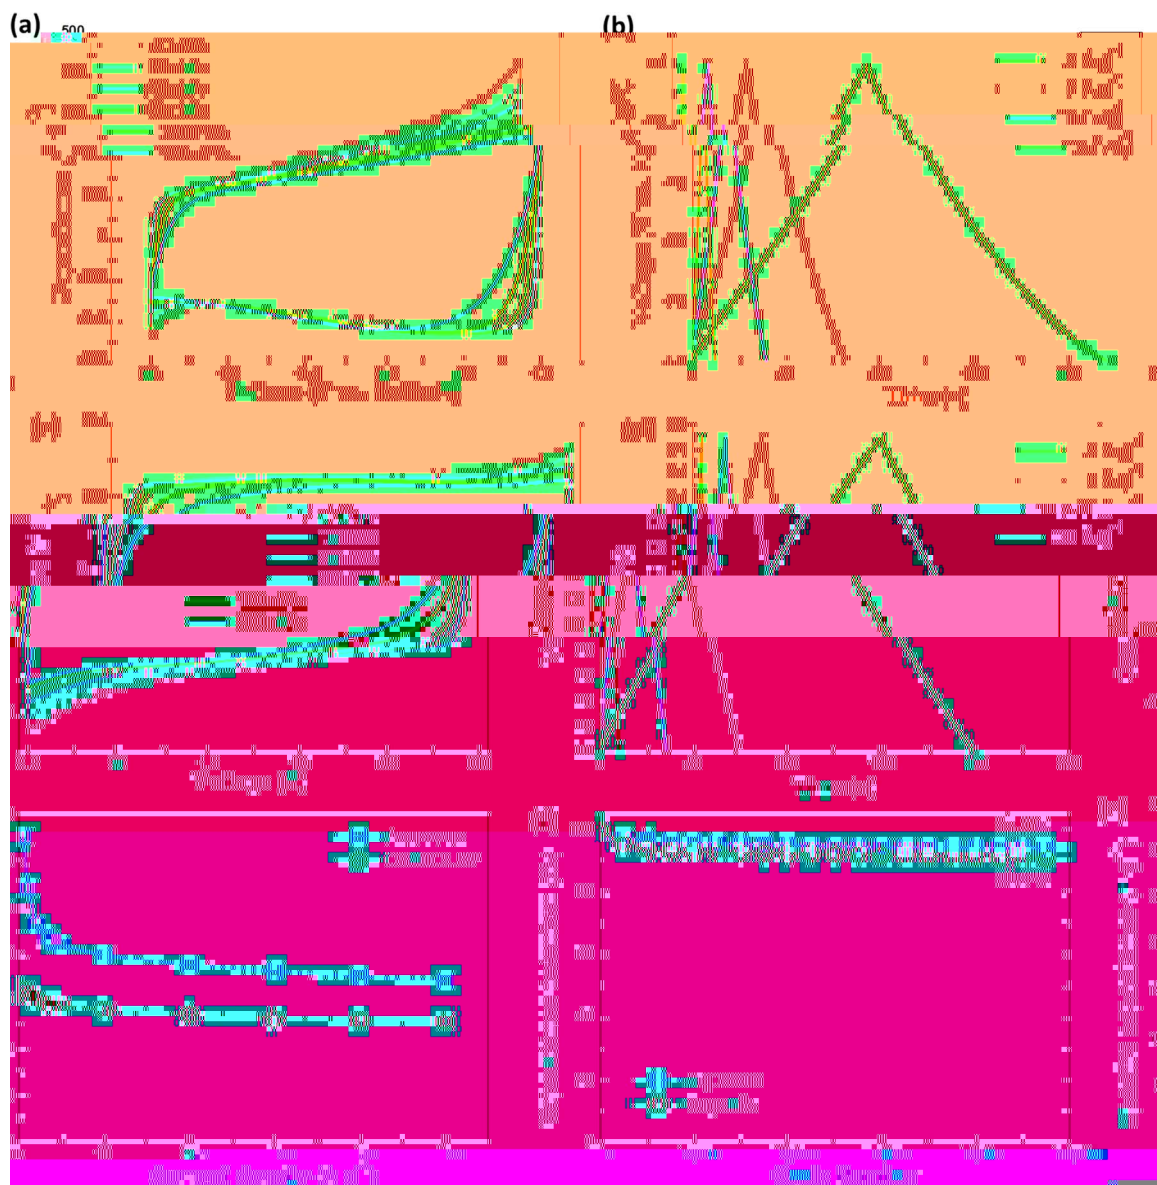


Fig. 3. EDLC performance of C800 tested in 6 M KOH electrolyte using a three-electrode configuration: (a) cyclic voltammetry at various scan rates; (b) galvanostatic charging/discharging curves at different current densities; EDLC performance of C800 tested in 1 M TEABF₄/AN electrolyte using a two-electrode configuration: (c) cyclic voltammetry at various scan rates; (d) galvanostatic charging/discharging curves at different current densities; (e) Specific

372 W kg⁻¹ when tested at 3 V. C800 retains an energy density of 21 W h kg⁻¹ even at a high power density of 30 kW kg⁻¹ when tested at 3 V. The energy density is one order of magnitude higher than that of commercial EDLCs, without losing the power capability. The performance of C800 is competitive when compared to the best values recently reported for carbon materials used in EDLCs with comparable voltage range [10,18,22,50,52,54,59–70]. Therefore, a high specific surface area combined with a high mesopore volume proportion is essential for a porous carbon material used in EDLCs for achieving superior performance.

We propose a qualitative model of ion migration to explain why the hierarchically meso-/microporous carbon material with optimized mesopores enables to perform ultra-high rate capability, in contrast with a solely microporous carbon material to perform lower rate capability. In a solely microporous carbon material, the average pore width is not much larger than the diameter of the solvated ions of

tetraethylammonium (TEA⁺) or tetrabutylammonium (TBA⁺). As shown on the left of Fig. 4b, typical porous carbon material contains high aspect-ratio slit-type pores which are deep and narrow. During charging/discharging, counterions migrate towards/away from the charged surface through these deep and narrow micropores at a limited velocity. At a high charging/discharging rate, the migration of counterions in the micropores lags behind the charge flow in/out of the electrode, leading to reduction of the capacitance. Also, the micropores tend to trap cations inside the pores, causing the reduction of the net charge density and the capacitance [71]. In contrast, when mesopores are created by connecting neighboring micropores as shown on the right of Fig. 4b, the depth of the micropores is greatly reduced. Ions migrating within this meso-/microporous structure experience much lower resistance and can travel from/to the charged surface quickly. Also, the possibility of cations being trapped inside slit-like micropores or mesopores is much reduced. Therefore, the capacitance in this




Fig. 4. (a) Ragone plot of C800 and commercial YP50 as supercapacitor electrodes in organic electrolyte, in comparison to recently reported values (Note: Only values from EDLCs, i.e., non-aqueous electrolytes, were selected for comparison, with a voltage window no wider than 3 V were selected from the literature); (b) Comparison of ion transport mechanisms and meso-/micro-porous materials.

meso-/micro-porous structure can be retained even at a very high charging/discharging rate. Both a high energy density and a high power density can be achieved simultaneously with the meso-/micro-porous structure proposed.

4. Conclusions

In summary, we developed a new class of polysiloxane-derived carbon materials with a large mesopore volume and a very high surface area contributed by its hierarchical meso-/micro-porosity. Different from conventional activated carbon materials with a high specific surface area but mostly micropores, polysiloxane-derived carbon materials contain mostly mesopores. The silica nanodomains in the SiOC ceramic derived from pyrolysis of polysiloxane prelay as an ~ 100 nm template to form mesopores in the final carbon product. Potentially, the pore structure of the final carbon product can be tuned by tailoring the formula of the polysiloxane precursor. The hierarchical meso-/micro-porosity facilitates fast transport of molecules and ions between the internal surface and outside environment, maximizing the effective surface area of the material in various applications. Owing to its mesoporosity, polysiloxane-derived carbon displayed superior rate performance in EDLCs with an organic electrolyte. The specific capacitance at a current density of 50 A g^{-1} was 80% of the specific capacitance at a current density of 0.5 A g^{-1} . The polysiloxane-derived

carbon achieved a maximum energy density of 42 Wh kg^{-1} and a maximum power density of 30 kW kg^{-1} , which were significantly higher than those of the commercial YP50 activated carbon.

In addition, we verified that the NaOH activation process can be extended to other polysiloxane materials. Using a similar processing protocol, carbon with the same high specific surface area and high mesopore volume was prepared from a single-component polysiloxane. We anticipate that this class of polysiloxane-derived carbon material will be a promising addition to the porous carbon materials family to further enhance the materials performance in many applications.

Acknowledgements

This research was financially supported by the National Materials Genome Project (2016YFB0700600), the Guangdong Innovation Team Project (No. 2013N080), and the Shenzhen Science and Technology Research Grants (No. JCYJ20150626110958181, JCYJ20150518092933435).

Appendix A. Supporting information

Supplementary data associated with this article can be found in the online version at doi:10.1016/j.nanoen.2017.02.007.

References

- [1] J. Yan, Q. Wang, T. Wei, Z. Fan, Recent advances in design and fabrication of electrochemical supercapacitors with high energy densities, *Adv. Energy Mater.* (2014) 1300816.
- [2] A. Burke, Ultracapacitors: why, how, and where's the technology, *J. Power Sources* 91 (2000) 37–50.
- [3] M.D. Stoller, S. Park, Y. Zhu, J. An, R.S. Ruoff, Graphene-based ultracapacitors, *Nano Lett.* 8 (2008) 3498–3502.
- [4] A.G. Parodofo, A.F. Hollnagel, Carbon properties and their role in supercapacitors, *J. Power Sources* 157 (2006) 11–27.
- [5] M. Wang, X. Song, S. Dai, W. Xu, Q. Yang, J. Li, C. Hu, D. Wei, NiO nanorattles supported on graphene 3D network current collector for high performance electrochemical energy storage, *Electrochim. Acta* 214 (2016) 68–75.
- [6] A. Burke, R&D considerations for the performance and application of electrochemical capacitors, *Electrochim. Acta* 53 (2007) 1083–1091.
- [7] Y. Jin, K. Tian, L. Wei, X. Zhang, X. Guo, Hierarchical porous microspheres of activated carbon with a high surface area for supercapacitors, *J. Mater. Chem. A* (2016).
- [8] T. Kim, G. Jung, S. Yoo, K.S. Kim, R.S. Ruoff, Activated graphene-based carbons as supercapacitor electrodes with macro- and mesopores, *ACS Nano* 7 (2013) 6899–6905.
- [9] J. Xu, Z. Tan, W. Zeng, G. Chen, S. Wu, Y. Zhao, K. Ni, Z. Tao, M. Li, H. Jia, Ni₃(S₂)₂(OH)₂(XO₂)₂-3DZr electrodes for flexible supercapacitors, *ACS Nano* 10 (2016) 3311–3321.

- [62] Q. Li, R. Jiang, Y. Dou, Z. Wu, T. Huang, D. Feng, J. Yang, A. Yu, D. Zhao, Synthesis of mesoporous carbon spheres with hierarchical pore structure for the electrochemical double-layer capacitor, *Carbon* 49 (2011) 1248–1257.
- [63] Y. Li, G. Wang, T. Wei, Z. Fan, P. Yan, Nitrogen and sulfur co-doped porous carbon nanosheets derived from willow catkins for supercapacitors, *Nano Energy* 19 (2016) 165–175.
- [64] Q. Liang, L. Ye, Z.-H. Huang, Q. Xu, Y. Bai, F. Kang, Q.-H. Yang, A honeycomb-like porous carbon derived from polyimide for use as a high-performance supercapacitors, *Nanoscale* 6 (2014) 13831–13837.
- [65] Y. Liang, F. Liang, H. Zhang, Z. Li, R. Li, D. Wu, An advanced carbonaceous porous network for high-performance organic electrolyte supercapacitors, *J. Mater. Chem. A* 1 (2013) 7000.
- [66] C. Long, X. Chen, L. Jiang, L. Zhi, Z. Fan, Porous layer-stacking carbon derived from a high temperature biomass for high volumetric performance supercapacitors, *Nano Energy* 12 (2015) 141–151.
- [67] D. Rujassri, V. Aravindan, S. Madhavi, S. Ogale, 3D microporous conducting carbon beeby by single step polymer carbonization for high-performance supercapacitors: the magic of the sulfur-oxygen formation, *Energy Environ. Sci.* 7 (2014) 728–735.
- [68] W. Sun, S.M. Hossain, C. Swartz, D. Williams, F. Yang, Hemp-derived activated carbons for supercapacitors, *Carbon* 103 (2016) 181–192.
- [69] K. Wang, Y. Cao, X. Wang, Q. Fan, W. Gibbons, T. Johnson, B. Luo, Z. Gu, Pyrolytic cyanobacteria derived activated carbon as high-performance electrode in symmetric supercapacitor, *Energy* 94 (2016) 666–671.
- [70] Q. Xie, A. Zhang, S. Zhai, S. Wu, C. Xie, Y. Zhang, Y. Guan, Reed straw derived active carbon/graphene hybrids as sustainable high-performance electrodes for advanced supercapacitors, *J. Solid State Electrochem.* 20 (2016) 449–457.
- [71] A.J. Pak, G.S. Hwang, Curing rate dependence of ion migration and stagnation in ionic-liquid-filled carbon nanotubes, *J. Phys. Chem. C* 120 (2016) 24560–24567.



Jie Yang received his Bachelor's degree in materials science and engineering from Harbin University, China, in 2014. He is currently a master's degree in the School of Advanced Materials, Peking University, China. His main research interests include advanced carbon materials for energy storage and conversion such as supercapacitors, lithium-ion batteries and metal-air batteries.



Wenju Ren received his Master's degree in 2008 from Yanshan University, China. He is currently a PhD student in Peking University Shenzhen Graduate School. His research is mainly focused on synthesizing nanomaterials and studying their properties for LIBs.



Prof. Yuan Lin, Institute of Chemistry, Chinese Academy of Sciences, got B.S. from Dept. Chemistry, Peking University in 1985, M.S and Ph.D. from Chinese Academy of Sciences (CAS) in 1988 and 1995, respectively. In 1988–1999, he took the position of assistant professor at Institute of Photographic Chemistry, Chinese Academy of Sciences. From 1999 to present, he took the position of full professor. For more than 20 years, Prof. Lin has been engaged in the fields of photoelectrochemical conversion of solar energy, preparation of nanocrystalline semiconductors, investigation of photoelectrochemical and surface properties of nanocrystalline semiconductors, developing ionic liquid and polymeric materials for electrolytes.



Haibiao Chen is currently a senior researcher at the School of Advanced Materials, Peking University Shenzhen Graduate School. He received his Bachelor's degree from Tsinghua University in 2000 and Ph.D. from Stevens Institute of Technology in 2006. He worked at Velbys during 2006–2011 and UES during 2011–2014 prior to joining Peking University Shenzhen Graduate School.



Haolin Wu received his Bachelor's degree from South China University of Technology, China, in 2014. He received his Master's degree in the School of Advanced Materials, Shenzhen Graduate School. He was working on developing ceramics and carbon materials for supercapacitors and lithium-ion batteries. Currently he is an employee of the China Development Bank.



Prof. Feng Pan, National 1000 Plan Professor, Founding Dean of School of Advanced Materials, Peking University Shenzhen Graduate School, Director of National Center of Electric Vehicle Power Battery and Materials for International Research, got B.S. from Dept. Chemistry, Peking University in 1985 and Ph.D. from Dept. of P&A Chemistry, University of Strathclyde, Glasgow, UK, with "Patrick D. Ritchie Prize" for the best Ph.D. in 1994. With more than a decade experience in large international corporations, Prof. Pan has been engaged in fundamental research and product development of novel photoelectronic and energy storage materials and devices. As Chief Scientist, Prof. Pan led 8 entities in Shenzhen to win the 150 million RMB grant for the national new energy vehicles (power battery) innovation project from 2013 to end of 2015. As Chief Scientist, Prof. Pan led 12 entities to win National Key project of Material Genome Engineering for Solid State Lithium Battery in China in 2016.



Min Zhu received his Bachelor's degree (BE) in 2015 from Tsinghua University. He is currently a master student major in materials chemistry in Peking University Shenzhen Graduate School. His research is mainly focused on porous materials and anode materials for lithium-ion batteries.